

TECHNICAL REPORT ARCCB-TR-96012

ISOTHERMAL BAINITE IN AF1410

**GREGORY N. VIGILANTE
PAUL J. COTE
TAMMY HICKEY
S. K. PAN**

APRIL 1996



**US ARMY ARMAMENT RESEARCH,
DEVELOPMENT AND ENGINEERING CENTER
CLOSE COMBAT ARMAMENTS CENTER
BENÉT LABORATORIES
WATERVLIET, N.Y. 12189-4050**




APPROVED FOR PUBLIC RELEASE; DISTRIBUTION UNLIMITED

19960730 124

DTIC QUALITY INSPECTED 1

DISCLAIMER NOTICE

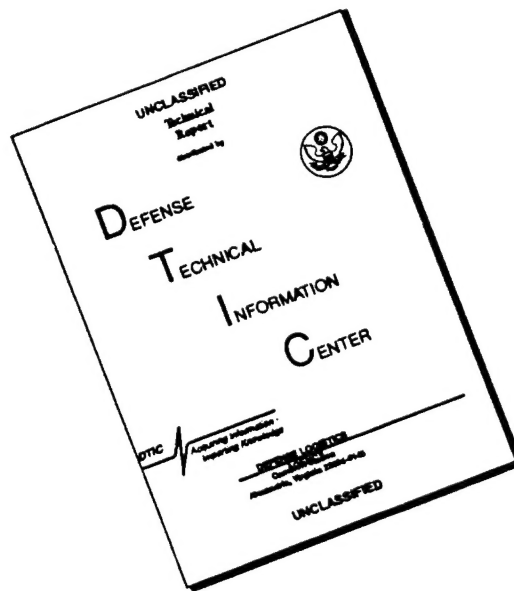

THIS DOCUMENT IS BEST QUALITY AVAILABLE. THE COPY FURNISHED TO DTIC CONTAINED A SIGNIFICANT NUMBER OF PAGES WHICH DO NOT REPRODUCE LEGIBLY.

DISCLAIMER

The findings in this report are not to be construed as an official Department of the Army position unless so designated by other authorized documents.

The use of trade name(s) and/or manufacturer(s) does not constitute an official indorsement or approval.

DESTRUCTION NOTICE

For classified documents, follow the procedures in DoD 5200.22-M, Industrial Security Manual, Section II-19 or DoD 5200.1-R, Information Security Program Regulation, Chapter IX.

For unclassified, limited documents, destroy by any method that will prevent disclosure of contents or reconstruction of the document.

For unclassified, unlimited documents, destroy when the report is no longer needed. Do not return it to the originator.

REPORT DOCUMENTATION PAGE

Form Approved
OMB No 0704-0188

Public reporting burden for this collection of information is estimated to average 1 hour per response, including the time for reviewing instructions, searching existing data sources, gathering and maintaining the data needed, and completing and reviewing the collection of information. Send comments regarding this burden estimate or any other aspect of this collection of information, including suggestions for reducing this burden, to Washington Headquarters Services, Directorate for Information Operations and Reports, 1215 Jefferson Davis Highway, Suite 1204, Arlington, VA 22202-4302, and to the Office of Management and Budget, Paperwork Reduction Project (0704-0188), Washington, DC 20503.

1. AGENCY USE ONLY (Leave blank)		2. REPORT DATE April 1996		3. REPORT TYPE AND DATES COVERED Final	
4. TITLE AND SUBTITLE ISOTHERMAL BAINITE IN AF1410				5. FUNDING NUMBERS AMCMS No. 6111.02.H611.1	
6. AUTHOR(S) Gregory N. Vigilante, Paul J. Cote, Tammy Hickey, and S.K. Pan					
7. PERFORMING ORGANIZATION NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Benet Laboratories, AMSTA-AR-CCB-O Watervliet, NY 12189-4050				8. PERFORMING ORGANIZATION REPORT NUMBER ARCCB-TR-96012	
9. SPONSORING/MONITORING AGENCY NAME(S) AND ADDRESS(ES) U.S. Army ARDEC Close Combat Armaments Center Picatinny Arsenal, NJ 07806-5000				10. SPONSORING/MONITORING AGENCY REPORT NUMBER	
11. SUPPLEMENTARY NOTES Presented at the Materials Research Society Fall Meeting, Boston, MA, 27 November to 1 December 1995. Published in Proceedings of the Meeting.					
12a. DISTRIBUTION AVAILABILITY STATEMENT Approved for public release; distribution unlimited.				12b. DISTRIBUTION CODE	
13. ABSTRACT (Maximum 200 words) The isothermal bainite transformation was identified in AF1410 by the use of thermomagnetic analysis methods. The formation of isothermal bainite in AF1410 has not been previously reported. Mechanical property test results indicate that isothermally processed AF1410 containing a mixture of bainite and martensite exceeds toughness properties of conventionally processed material containing 100% martensite. Moreover, the yield strength of isothermally processed material is the same as conventionally processed material. Because the isothermal transformation to bainite occurs gradually over time, large internal strains are avoided. This contrasts with athermal martensite transformations where the rapid martensite transformation upon quenching often leads to distortion and cracking. The isothermal bainite in AF1410 can be exploited through the use of current isothermal processing methods to facilitate fabrication of the alloy. Isothermal processing of AF1410 components may permit most of the machining operations to be completed in the annealed condition (Rc 36) rather than in the peak aged condition (Rc 48).					
14. SUBJECT TERMS Bainite, AF1410, Isothermal Heat Treatments, Kinetics, Mechanical Properties, Producibility, Ultra-High Strength Steels				15. NUMBER OF PAGES 16	
				16. PRICE CODE	
17. SECURITY CLASSIFICATION OF REPORT UNCLASSIFIED	18. SECURITY CLASSIFICATION OF THIS PAGE UNCLASSIFIED	19. SECURITY CLASSIFICATION OF ABSTRACT UNCLASSIFIED	20. LIMITATION OF ABSTRACT UL		

TABLE OF CONTENTS

	<u>Page</u>
INTRODUCTION	1
EXPERIMENTAL PROCEDURE	1
Isothermal Tests	1
Kinetics	2
Mechanical Property Tests	2
DISCUSSION	2
Isothermal Tests	2
Kinetics	3
Comments on Activation Energies	4
Mechanical Property Tests	5
SUMMARY	6
REFERENCES	7

TABLES

1.	Chemical composition of AF1410 (wt. %)	9
2.	Typical mechanical property results on conventionally processed AF1410	10
3.	Preliminary mechanical property results on conventionally processed AF1410 vs. isothermally processed AF1410	11

LIST OF ILLUSTRATIONS

1.	Heat treatments used for preliminary mechanical property tests	12
2.	Isothermal bainite transformation curves for AF1410	13
3.	Isothermal bainite transformation curves for AF1410	14
4.	Johnson-Mehl-Avrami plots of isothermal transformations in AF1410	15

INTRODUCTION

The isothermal bainite transformation was identified in AF1410 through the use of Benét's Thermomagnetic Analyzer developed by Cote et al.^[1] The formation of isothermal bainite in AF1410 has not been previously reported. Mechanical property test results indicate that isothermally processed AF1410 containing a mixture of bainite and martensite exceeds toughness properties of conventionally processed material containing 100% martensite with little sacrifice in strength.

AF1410 is characterized as an ultra high-strength steel (typically 1720 MPa tensile strength). This alloy was developed under Air Force sponsorship and has been used in critical applications such as airframe structural components, landing gear components, light armor plate, etc., where high strength and toughness are crucial. Secondary carbides, which precipitate in AF1410 during aging, give the alloy its high strength and consequently, make the alloy difficult to machine.

The isothermal bainite in AF1410 can be exploited through the use of current isothermal processing methods, e.g., molten salt baths, to facilitate fabrication of the alloy. Isothermal processing of AF1410 components may permit most of the machining operations to be completed in the full annealed condition (Rc 36) rather than in the peak aged condition (Rc 48). Additionally, potential distortion and cracking problems are avoided because isothermal processing is a gentle process that produces little distortion. Most important, the benefits of isothermal processing on AF1410 can be achieved without sacrificing in mechanical properties.

The chemistry and mechanical properties of AF1410 are provided in Tables 1 and 2. Extensive studies exploring isothermal bainite transformations have been conducted by Benét Laboratories.^[1-4]

EXPERIMENTAL PROCEDURE

Test material for this study came from a hollow forging of AF1410 (4.5" I.D., 6.4" O.D., 11 ft. long). Pins 3/4" in length and 1/8" in diameter were fabricated from the forged material.

Isothermal Tests

All isothermal tests are conducted with pins electroplated with copper to protect the surface from oxidation and decarburization. Additional protection against oxidation is gained by conducting all tests in a 90% He/10% H₂ reducing atmosphere.

Test specimens are austenitized at 830°C for 10 minutes to fully transform the microstructure to austenite, a non-ferromagnetic phase. Test specimens are suspended in the austenitizing furnace by a fine chromel thermocouple wire. After austenitizing, the specimens are lowered into a "quench block" in the Thermomagnetic Analyzer. This is an essential feature of the system because it rapidly cools the specimens and avoids the otherwise slow asymptotic cooling to the isothermal temperature that can cause the formation of undesirable austenite

decomposition products. Upon placement in the quench block, a second thermocouple lead (alumel) is inserted through a small radial hole in the quench block to secure the specimens within the quench block and to dynamically monitor the cooling of the specimens. When the temperature of the cooling specimens is 40°C greater than that of the isothermal target temperature, the radial thermocouple is removed, allowing the specimens to be dropped into the isothermal furnace. This temperature discrepancy was experimentally developed to allow for further cooling of the specimen as it is dropped into the isothermal furnace. The in-situ isothermal transformation is monitored by measuring the change in the magnetization of the material (paramagnetic austenite to ferromagnetic bainite and martensite). The transformation time and magnetic response of the specimens is recorded on a PC for later data analysis. More detailed information regarding the Thermomagnetic Analyzer can be found in Reference 1.

The isothermal transformation studies were conducted at temperatures ranging from 280°C to 370°C in 10°C increments. Two additional tests were conducted at 220°C and 250°C.

Kinetics

All isothermal data were analyzed assuming Johnson-Mehl-Avrami (JMA) kinetics. JMA analysis has been extensively used in isothermal transformations to determine the mechanism(s) controlling nucleation and growth characteristics.

Mechanical Property Tests

Preliminary mechanical property tests were conducted on AF1410 material to compare the strength and toughness of conventionally processed material to isothermally processed material. Figure 1 shows two of the heat treatments examined in this experiment. Heat treatments were conducted on small test coupons of AF1410 material. The isothermal processing was conducted using two interconnected furnaces. After the test material was austenitized, it was transferred into an isothermal furnace. The mechanical properties examined included tensile, Charpy v-notch, and fracture toughness (J_{Ic}) tests. Charpy and fracture toughness tests were conducted at both RT and -40°C.

DISCUSSION

Isothermal Tests

Data from all isothermal transformation studies were analyzed to determine the volume fraction transformed versus time. The volume fraction transformed is related to the magnetic reading by the following relationship:

$$V_{fx} = \frac{M_0 - M_a}{M_{100} - M_0} \quad (1)$$

where V_{fx} is the volume fraction transformed, M_0 is the minimum magnetization reading (representing 100% austenite), M_a is the actual magnetization reading at a given time increment, and M_{100} is the maximum magnetization reading (representing 100% martensite). The magnetic response is a sensitive function of the specimen length-to-diameter ratio (l/d). The present specimen geometry was selected to produce the linear relationship between the volume fraction transformed and the magnetic response as given in the above equation.

Figure 2 shows the isothermal transformation curves of AF1410 in the range of temperatures tested. Above 320°C, the curves were sigmoidal in appearance, representative of the nucleation, growth, and subsequent impingement of the transformation product. The incomplete transformation phenomenon was observed: As the temperature increased, less product transformed. These features are characteristic to both the isothermal bainite and isothermal martensite transformation. Figure 3 contains the identical curves as Figure 2, except that the abscissa has been magnified in order to observe the initial stages of the transformation. The tests conducted below 320°C revealed an instantaneous transformation. Also, below 320°C, the characteristic sigmoidal features are not present. These observances are attributed to the instantaneous formation of a small fraction of athermal martensite that caused increased nucleation and growth of the isothermal bainite. It is apparent, therefore, that the martensite start (M_s) temperature of AF1410 is approximately 320°C. This value for M_s corresponds reasonably well to that described in the literature [5, 6], in which M_s was reported in the range of 300-335°C. Thus, it is determined that the transformations occurring in AF1410 alloy are isothermal bainite and not isothermal martensite. Metallography was conducted to corroborate the formation of bainite as evidenced by the thermomagnetic test results; however, the results are inconclusive.

Kinetics

The kinetics of the isothermal bainite transformation in AF1410 were analyzed using conventional JMA equations. Porter and Easterling [7] and Christian [8] provide excellent discussions of JMA kinetics. Interpretation of the JMA equation provides the user with information on the nucleation and growth mechanisms that control isothermal transformation. The JMA equation is expressed in the form:

$$X = 1 - \exp(-kt^n) \quad (2)$$

where X is the extended volume fraction of product phase formed at time t (expressed in seconds), k is a rate constant highly dependent on temperature ($k = A \exp^{-Q/RT}$, where A is a constant, Q is an activation energy, R is the gas constant and T is the absolute temperature), and n is a constant assumed to be independent of temperature. Rearranging equation (2) gives:

$$\log \ln[1/(1-X)] = n \log t + \log k \quad (3)$$

where n is the slope of the line and $\log k$ is the y-intercept. The kinetics of AF1410, as seen in

Figure 4, do not exhibit straight-line behavior over the majority of temperatures tested. It is evident, therefore, that JMA kinetics were not adequate in describing the nucleation and growth characteristics of the isothermal bainite transformation in AF1410.

The non-linearity of the JMA results in AF1410 is not unusual. Previous tests on plain carbon and alloys steels ^[9-12] show similar, though not as dramatic, deviations from the expected linear JMA results. The deviation in straight-line behavior is believed to be associated with a change in the average growth rate, which can be affected by both the nucleation rate and growth geometry. Additionally, when using the Avrami equation, a constant growth rate is inherently assumed.

The kinetics of AF1410 are complex because of the high percentage of alloying elements present. Chemical segregation (i.e., banding) may cause the nucleation and growth kinetics to become altered compared with homogeneous plain carbon steels. Further complications may be introduced by the type of segregated alloying elements present in the microstructure. For example, Co shifts the "C" curve to the left, while other alloying elements shift the "C" curve to the right.

Variations in solute concentration, grain size, etc., can alter the growth rate during the isothermal transformation and lead to non-JMA kinetics. This change in growth rate was addressed by both Rath ^[13] and Cahn and Hagel.^[14] Rath described JMA kinetics as being a subset of a more universal equation that describes more general isothermal transformations. In Rath's formulation, a variable growth rate is allowed. In using Rath's universal kinetic equation, isothermal transformations can be analyzed to determine if the growth rate is constant or variable. This equation may provide valuable insight on the kinetics of the isothermal bainite transformation in AF1410.

Comments on Activation Energies

It is well known that the transition from upper to lower bainite occurs universally at approximately 350°C. Therefore, it is postulated that examining the kinetics of the bainite transformation above and below this temperature will determine the activation energies for upper and lower bainite. Several experiments have been conducted ^[9-12] using a chemical rate equation based on equation (2). The derivative of equation (2) was taken to give an expression of the rate of the bainite transformation:

$$\frac{dX}{dt} = nkt^{n-1} \exp(-kt^n) = nkt^{n-1}(1-X) \quad (4)$$

so that:

$$\frac{dX}{dt} = C \exp^{-Q/RT} \quad (5)$$

where C is a function of X and independent of temperature, Q is the activation energy, R is the gas constant, and T is the absolute temperature.

These activation energies are not constants if the mechanisms for nucleation and/or growth change during the isothermal transformation, or if the mechanism(s) change during a temperature range of interest, i.e., if the slope of the JMA plot does not remain constant. In typical time-temperature-transformation (TTT) diagrams, "C" curves are produced because of two competing activation energies, an activation energy for nucleation (Q_n) and an activation energy for diffusional growth (Q_g). At high temperatures, nucleation is limited and diffusional growth is dominant; conversely, diffusional growth is limited and nucleation is dominant at low temperatures. The lowest activation energy is associated with an intermediate temperature at which both nucleation and growth are active. These competing nucleation and growth mechanisms lead to an overall activation energy that constantly changes with temperature. It is thus difficult to acknowledge the validity of the activation energies of upper and lower bainite experimentally determined when the slopes of the JMA plots did not remain constant. It may be feasible to perform tests where either the nucleation or growth mechanisms dominate. One method of accomplishing this is to conduct isothermal tests at sufficiently low temperatures to ensure early site saturation. Therefore, only the growth mechanism is monitored during the transformation. If the average growth rate and the shape of the growing phase do not change, a meaningful activation energy may be extracted.

Mechanical Property Tests

Table 3 contains the mechanical properties results for conventionally processed AF1410 (from product literature and actual testing conducted at Benét) compared with isothermally processed AF1410.

A slight decrease in the 0.2% yield strength (approximately 3%) of the isothermally processed material was measured compared with conventionally processed material. However, with the decrease in yield strength, there was a corresponding 10% increase in toughness at RT compared with conventionally processed material. All fracture toughness tests were J_{Ic} tests

conducted in accordance with ASTM E-813. These data were converted to K_J data by the relation:

$$K_J = \sqrt{\frac{EJ_{Ic}}{1-\nu^2}} \quad (6)$$

where E is Young's Modulus, J is the J-integral fracture toughness expressed in units of MN/m ($\text{in}\cdot\text{lb}/\text{in}^2$), and ν is poisson's ratio. K_J has the units of $\text{MPa}\sqrt{\text{m}}$ ($\text{ksi}\sqrt{\text{in}}$). Assuming the universal values for E and ν for steels of 207 GPa (30×10^6 psi) and 0.3, respectively, results in the following relationships:

$$\begin{aligned} K_J &= 477\sqrt{J_{Ic}} \quad (\text{MPa}\sqrt{\text{m}}) \\ K_J &= 5.74\sqrt{J_{Ic}} \quad (\text{ksi}\sqrt{\text{in}}) \end{aligned} \quad (7)$$

Further isothermal tests using molten salts are necessary before making firm conclusions.

SUMMARY

Isothermal bainite has not been previously reported in AF1410 alloy. Isothermal bainite was identified using thermomagnetic analysis. Isothermal test temperatures ranged from 220-370°C. Plots of volume fraction formed versus time revealed the typical sigmoidal shape common to isothermal bainite. The kinetics of the isothermal bainite transformation were examined using the JMA equation. Because the JMA plots were not linear, these equations were not sufficient to describe the nucleation and growth characteristics of isothermal bainite in AF1410. A more universal kinetic equation is currently being examined for the kinetics in AF1410.

Preliminary mechanical properties tests comparing isothermally processed material with conventionally processed material indicate no significant sacrifice in strength and an improvement in toughness in the isothermally processed material over the conventionally processed material.

The identification of isothermal bainite in AF1410 can be exploited through the use of current isothermal processing methods, e.g., molten salt baths, to facilitate fabrication of the alloy. Isothermal processing of AF1410 components will enable the majority of the machining operations to be completed in the full annealed condition (Rc 36) rather than in the peak aged condition (Rc 48). Additionally, potential distortion and cracking problems will be eliminated because isothermal processing produces little distortion. These benefits of isothermal processing on AF1410 can be achieved without sacrificing mechanical properties.

REFERENCES

1. Cote, P. J., Hickey, T., Witherall, M., "Application of a Rapid Quench Thermomagnetic Analyzer to Austempered Ductile Iron," ARDEC Technical Report #94044, Benét Laboratories, Watervliet, NY, 1994.
2. Cote, P. J., "Isothermal Bainite Processing of ASTM A723 Components," ARDEC Technical Report #93035, Benét Laboratories, Watervliet, NY, 1993.
3. Barranco, J. M., Cote, P. J., Kapp, J. A., "Tempering Effects for Lower Bainite, Martensite, and Mixed Microstructures on Impact, Fracture, and Related Mechanical Properties of ASTM A723 Steel," ARDEC Technical Report #92024, Benét Laboratories, Watervliet, NY, 1992.
4. Kapp, J. A., et al. "Unusually High Fracture Toughness of ASTM A723 Steel from a Mixed Martensite/Bainite Microstructure," ARDEC Technical Report #90032, Benét Laboratories, Watervliet, NY, 1990.
5. Unimach AF1410 Technical Data Sheet, Universal-Cyclops Specialty Steel Division, Pittsburgh, PA.
6. Ghosh, G. and Olson, G. B., "Kinetics of F.C.C. - B.C.C. Heterogeneous Martensitic Nucleation--I. The Critical Driving Force for Athermal Nucleation," *Acta Metallurgica.*, Vol. 42, No. 10, pp. 3361-3370, 1994.
7. Porter, D. A. and Easterling, K. E., *Phase Transformations in Alloys*, T. J. Press, 1981, pp. 287-290.
8. Christian, J. W., *The Theory of Transformations in Metals and Alloys*, Pergamon Press, 1965.
9. Radcliffe, S. V. and Rollason, E. C., "The Kinetics of the Formation of Bainite in High-Purity Iron-Carbon Alloys," *Journal of the Iron and Steel Institute*, January 1959, pp. 56-65.
10. White, J. S. and Owen, W. S., "Kinetic Features of Upper and Lower Bainite Formation in a Plain Carbon and 3%Ni-Cr Steel," *Journal of the Iron and Steel Institute*, May 1960, pp. 79-82.
11. Hawkins, M. J. and Barford, J., "Experimental Kinetics of Bainite Formation," *Journal of the Iron and Steel Institute*, February 1972, pp. 97-105.
12. Okamoto, H. and Oka, M., "Lower Bainite with Midrib in Hypereutectoid Steels," *Met. Trans. A.*, Vol. 17A, July 1986, pp. 1113-1120.

13. Rath, B. B., "The Overall Kinetics of the Isothermal Transformations," *Proceedings of an International Conference on Solid-Solid Phase Transformations*, Pittsburgh, PA, 1981, pp. 1097-1104.
14. Cahn, J. W. and Hagel, W. C., "Divergent Pearlite in a Manganese Eutectoid Steel," *Acta Metallurgica*, Vol. 11, June 1963, pp. 561-574.

Table 1. Chemical composition of AF1410 (wt. %)

Alloying Element	Typical Chemistry (wt. %)
C	0.16
Mn	0.01
Si	0.01
S	.005
P	.008
Cr	2.00
Ni	10.00
Co	14.00
Mo	1.00
Fe	Balance

Table 2. Typical mechanical property results on conventionally processed AF1410

Mechanical Properties	Product Literature Conventional H.T.*	Bénet Conventional H.T.
UTS MPa; [Ksi]	1620 [235]	1682 [244]
0.2% YS MPa; [Ksi]	1517 [220]	1524 [221]
Elongation	12%	-
%RA	60%	-
Charpy (RT) J; [ft•lb]	-	77 [57]
Charpy (-40) J; [ft•lb]	-	64 [47]
K _{IC} ** (RT) MPa√m; [Ksi√in]	143 [130]	210 [191]
K _{IC} ** (-40) MPa√m; [Ksi√in]	-	187 [170]

[] English Units

*Unimach AF1410 High Strength Steel Technical Data Sheet, Universal-Cyclops Specialty Steel Division, Pittsburgh, PA, 1978.

**In Bénet fracture tests J_Q data were converted to K_{IQ}.

Table 3. Preliminary mechanical property results on conventionally processed AF1410 vs. isothermally processed AF1410


Mechanical Properties	Product Literature Conventional H.T.*	Benét Conventional H.T.**	Benét Isothermal H.T.
UTS MPa; [Ksi]	1620 [235]	1682 [244]	1708 [248]
0.2% YS MPa; [Ksi]	1517 [220]	1524 [221]	1469 [213]
Elongation	12%	-	-
%RA	60%	-	-
Charpy (RT) J; [ft•lb]	-	77 [57]	79 [58]
Charpy (-40) J; [ft•lb]	-	64 [47]	66 [49]
K _{IC} ** (RT) Mpa√in; [Ksi√in]	143 [130]	210 [191]	230 [209]
K _{IC} ** (-40) Mpa√in; [Ksi√in]	-	187 [170]	-

[] English Units

*Unimach AF1410 High Strength Steel Technical Data Sheet, Universal-Cyclops Specialty Steel Division, Pittsburgh, PA, 1978.

**In Benét fracture tests J_Q data were converted to K_{IQ}.

AF1410 Conventional Heat Treatment: 900C 1hr Air Cool to RT
 840C 1hr Air Cool to RT
 510C 5hr Air Cool to RT

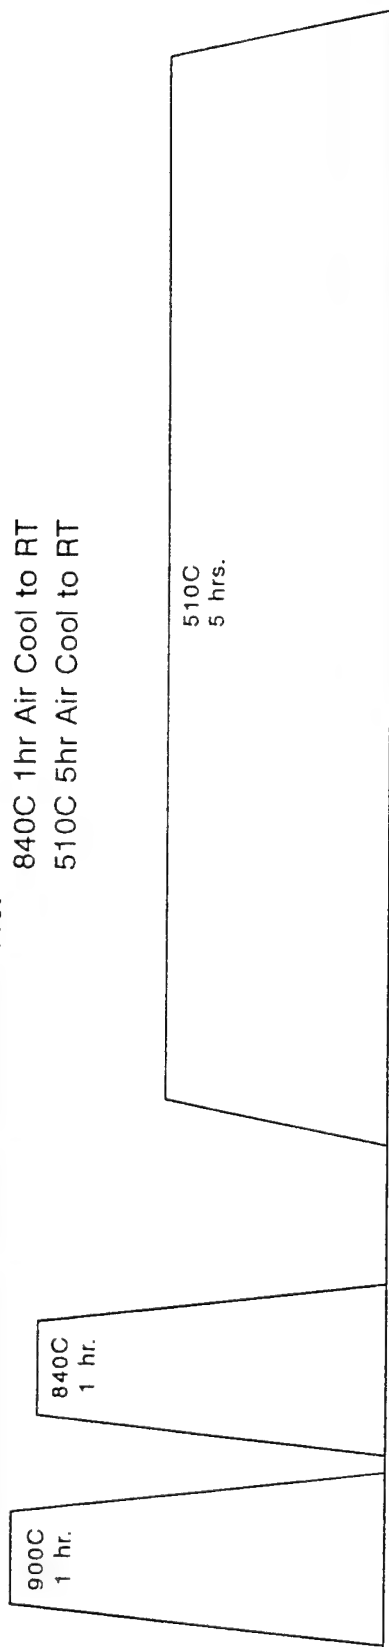

AF1410 Isothermal Heat Treatment: 900C 1hr Air Cool to RT
 840C 1hr Air Cool to
 300C 1hr Air Cool to RT
 510C 5hr Air Cool to RT

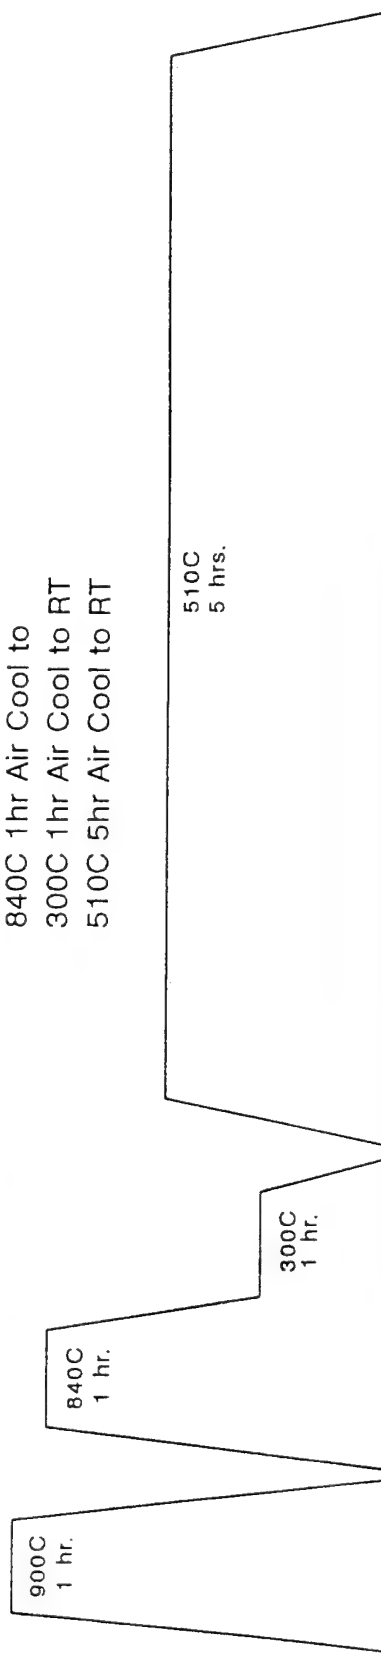


Figure 1. Heat treatments used for preliminary mechanical property tests

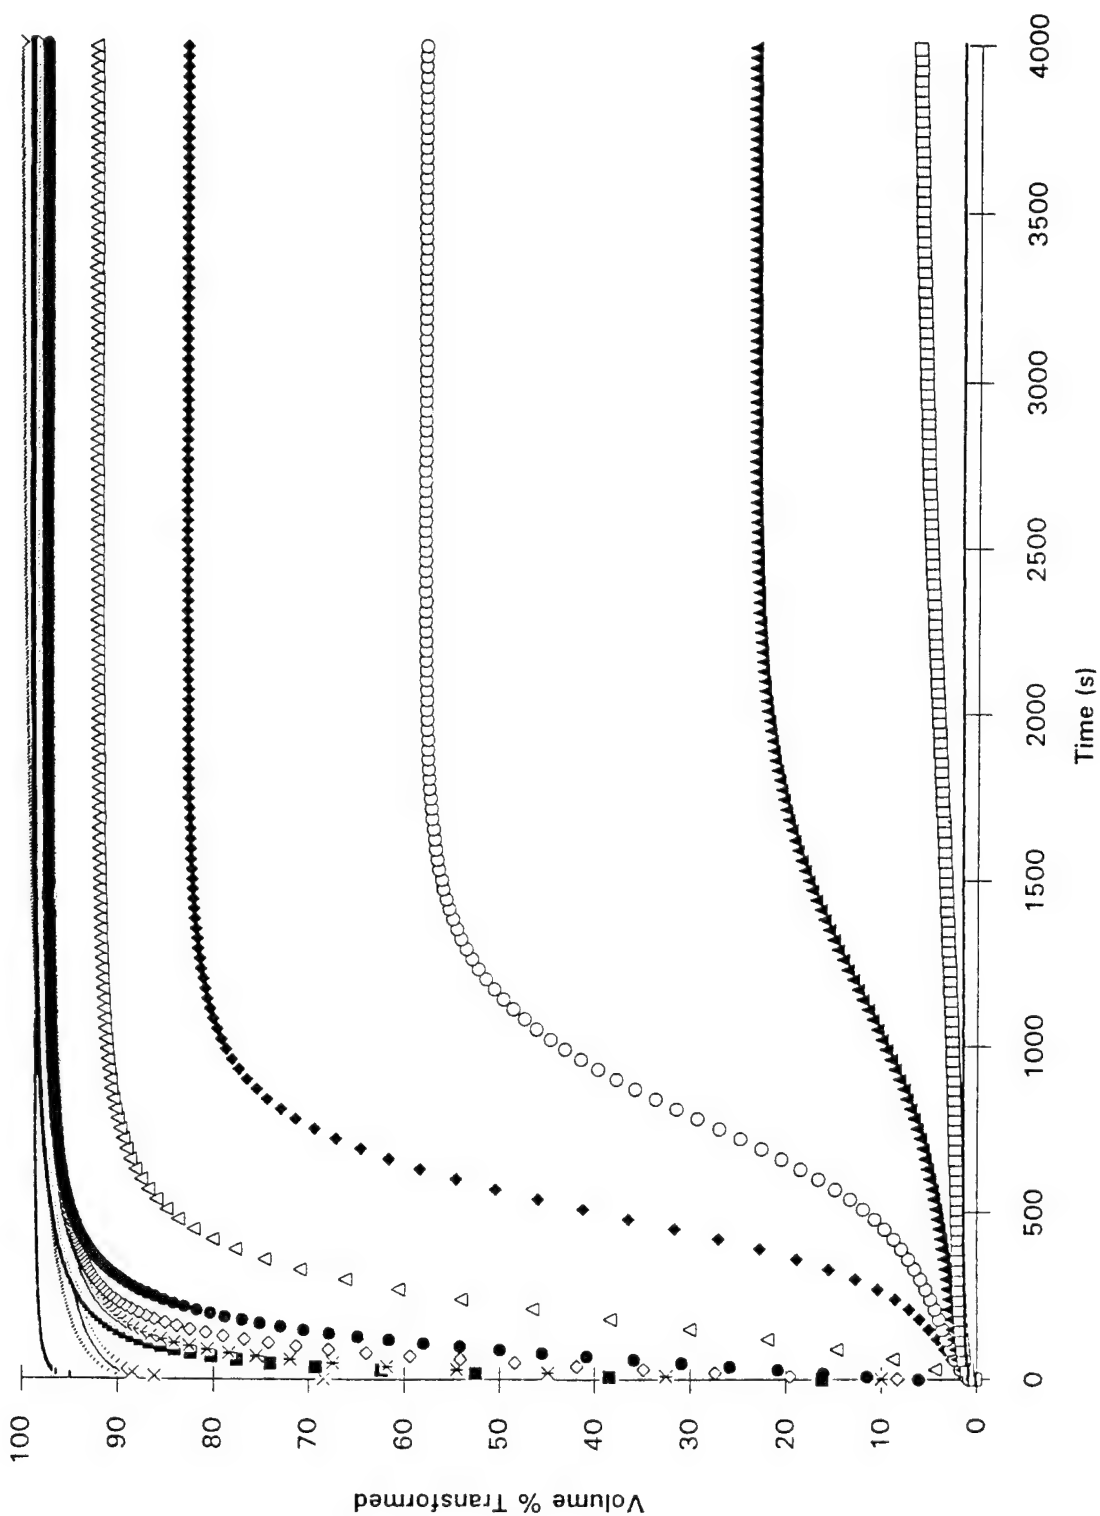


Figure 2. Isothermal bainite transformation curves for AF1410

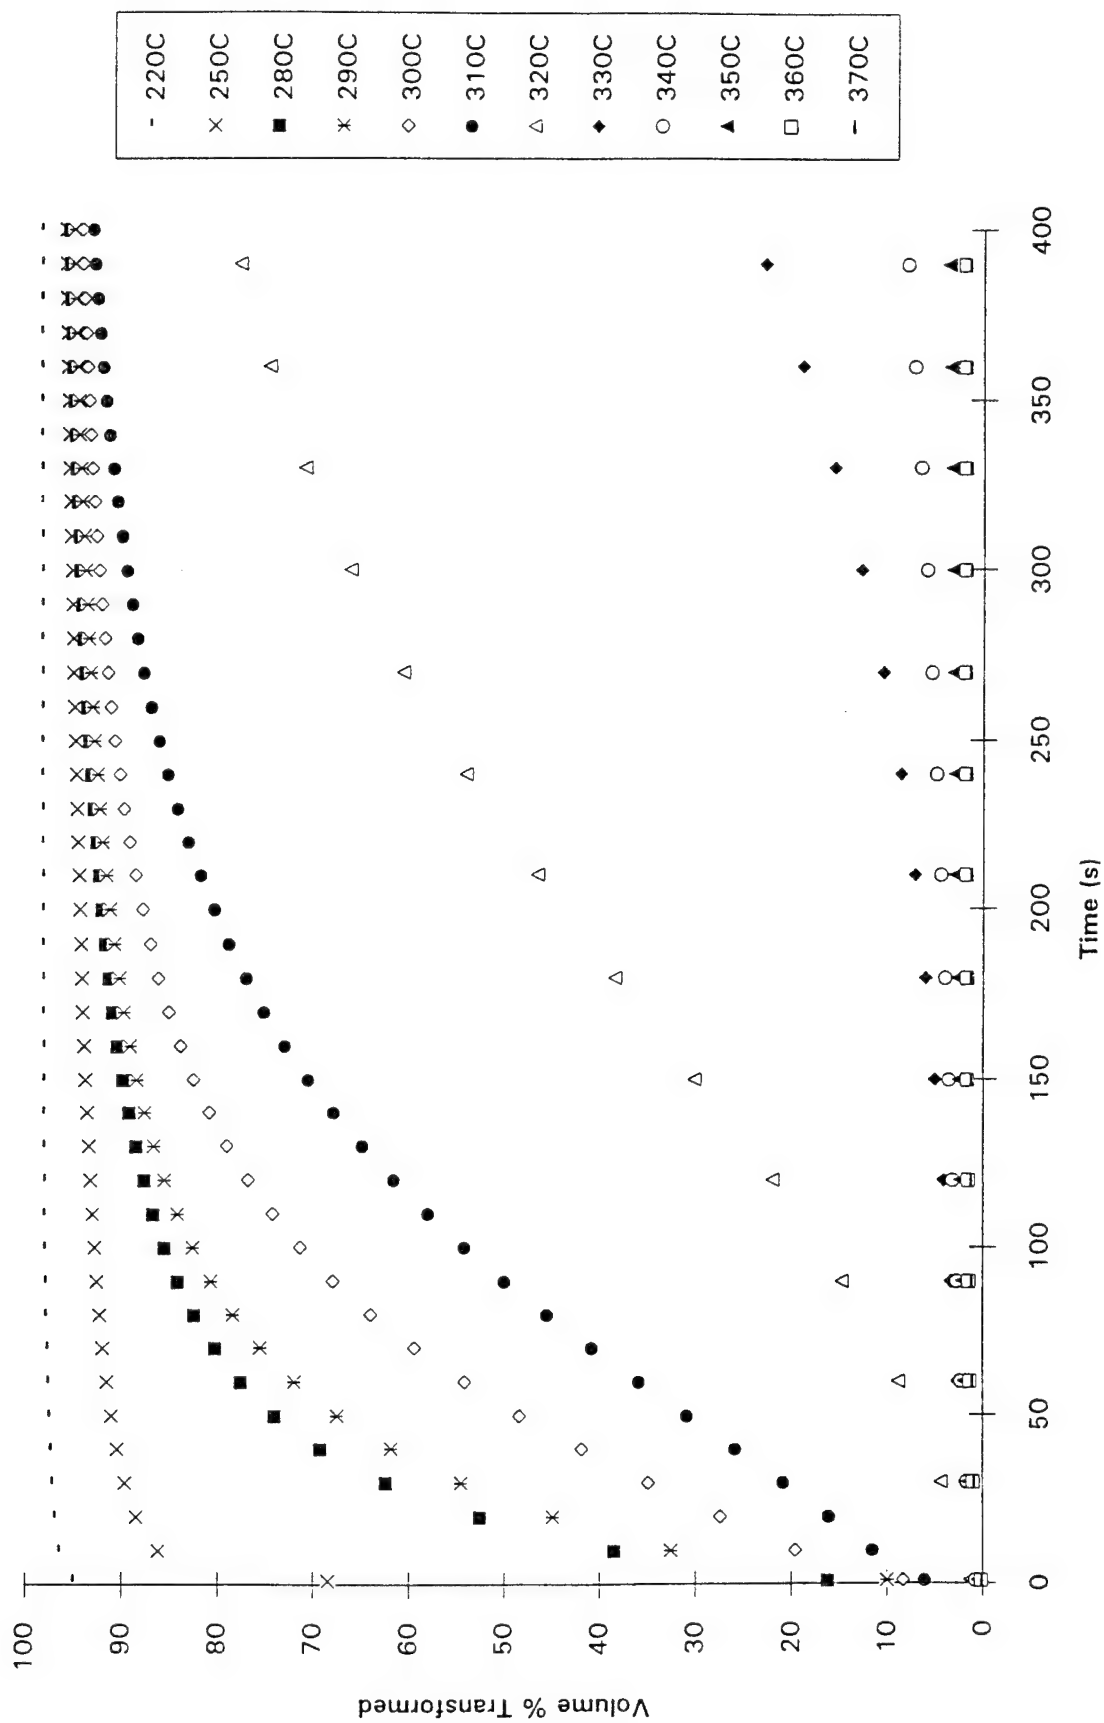


Figure 3. Isothermal bainite transformation curves for AF1410

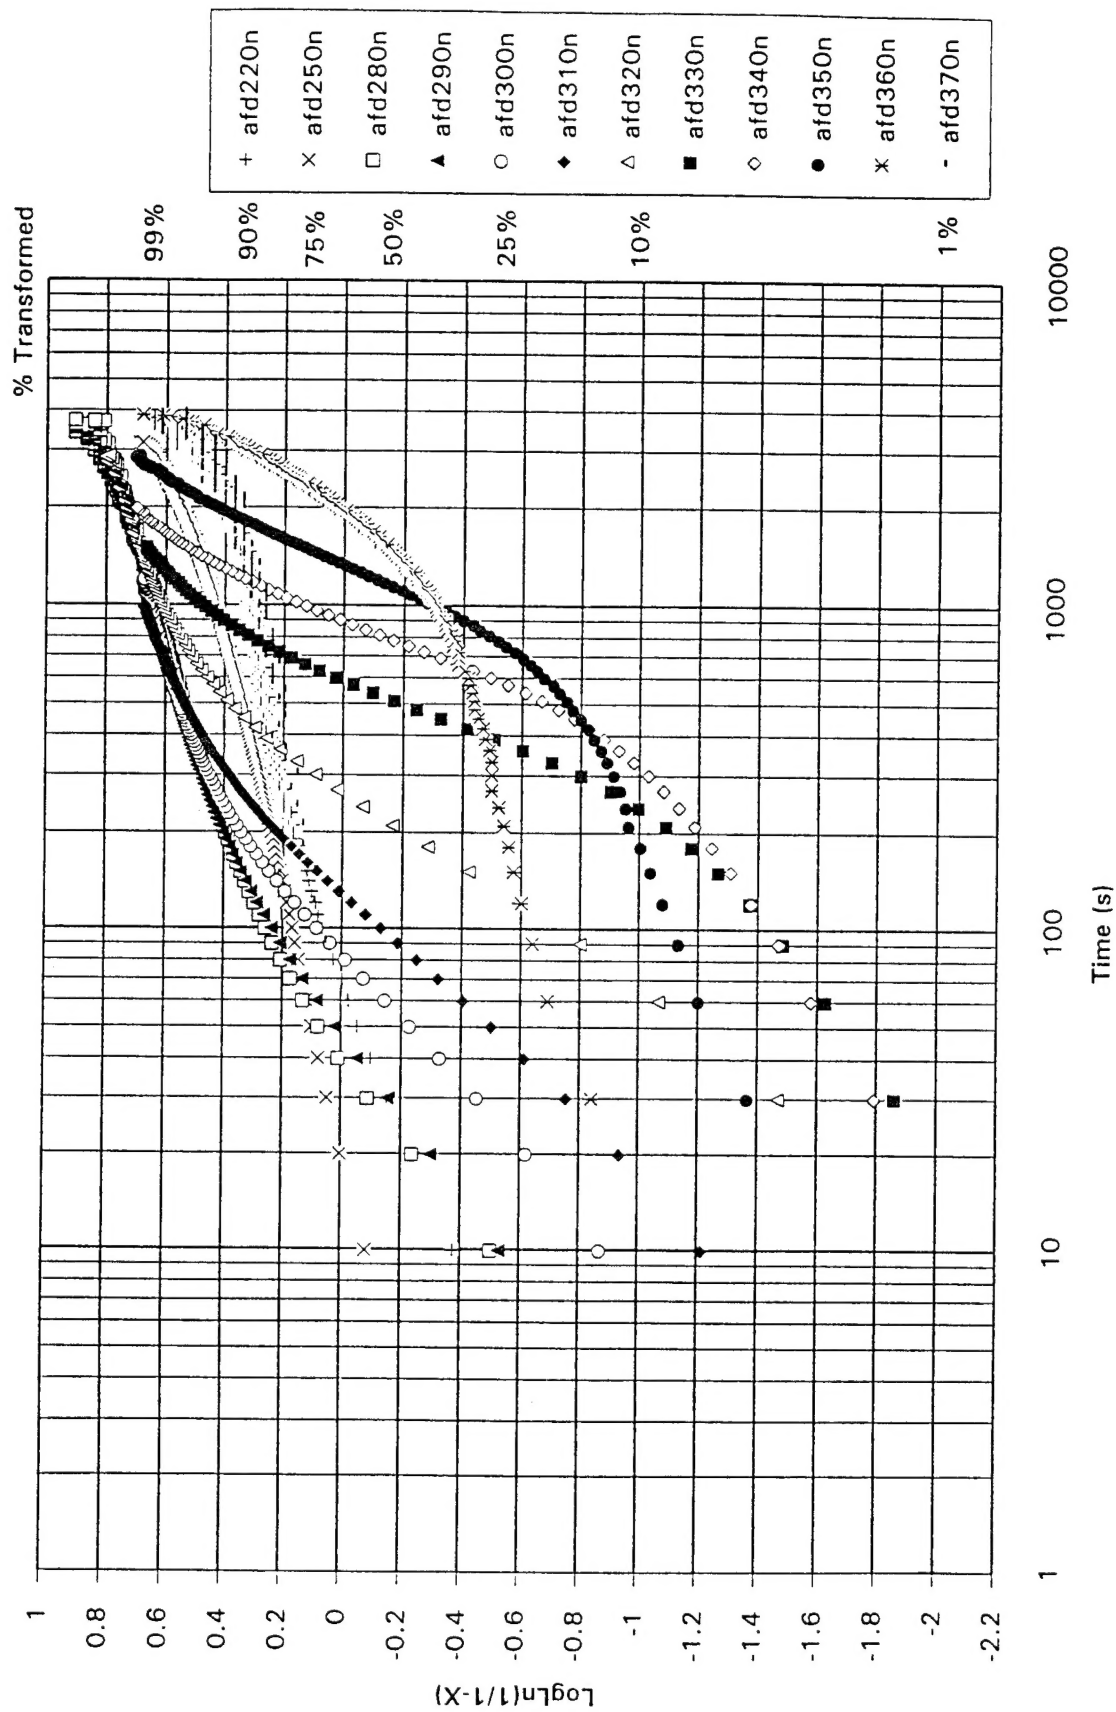


Figure 4. Johnson-Mehl-Avrami plots of isothermal bainite transformations in AF1410

TECHNICAL REPORT INTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>
CHIEF, DEVELOPMENT ENGINEERING DIVISION	
ATTN: AMSTA-AR-CCB-DA	1
-DB	1
-DC	1
-DD	1
-DE	1
CHIEF, ENGINEERING DIVISION	
ATTN: AMSTA-AR-CCB-E	1
-EA	1
-EB	1
-EC	1
CHIEF, TECHNOLOGY DIVISION	
ATTN: AMSTA-AR-CCB-T	2
-TA	1
-TB	1
-TC	1
TECHNICAL LIBRARY	
ATTN: AMSTA-AR-CCB-O	5
TECHNICAL PUBLICATIONS & EDITING SECTION	
ATTN: AMSTA-AR-CCB-O	3
OPERATIONS DIRECTORATE	
ATTN: SIOWV-ODP-P	1
DIRECTOR, PROCUREMENT & CONTRACTING DIRECTORATE	
ATTN: SIOWV-PP	1
DIRECTOR, PRODUCT ASSURANCE & TEST DIRECTORATE	
ATTN: SIOWV-QA	1

NOTE: PLEASE NOTIFY DIRECTOR, BENÉT LABORATORIES, ATTN: AMSTA-AR-CCB-O OF ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
ASST SEC OF THE ARMY RESEARCH AND DEVELOPMENT ATTN: DEPT FOR SCI AND TECH THE PENTAGON WASHINGTON, D.C. 20310-0103	1	COMMANDER ROCK ISLAND ARSENAL ATTN: SMCRI-SEM ROCK ISLAND, IL 61299-5001	1
DEFENSE TECHNICAL INFO CENTER ATTN: DTIC-OCF (ACQUISITIONS) 8725 JOHN J. KINGMAN ROAD STE 0944 FT. BELVOIR, VA 22060-6218	2	MIAC/CINDAS PURDUE UNIVERSITY 2595 YEAGER ROAD WEST LAFAYETTE, IN 47906-1398	1
COMMANDER U.S. ARMY ARDEC ATTN: AMSTA-AR-AEE, BLDG. 3022	1	COMMANDER U.S. ARMY TANK-AUTMV R&D COMMAND ATTN: AMSTA-DDL (TECH LIBRARY) WARREN, MI 48397-5000	1
AMSTA-AR-AES, BLDG. 321	1	COMMANDER U.S. MILITARY ACADEMY	
AMSTA-AR-AET-O, BLDG. 183	1	ATTN: DEPARTMENT OF MECHANICS	1
AMSTA-AR-FSA, BLDG. 354	1	WEST POINT, NY 10966-1792	
AMSTA-AR-FSM-E	1	U.S. ARMY MISSILE COMMAND	
AMSTA-AR-FSS-D, BLDG. 94	1	REDSTONE SCIENTIFIC INFO CENTER	2
AMSTA-AR-IMC, BLDG. 59	2	ATTN: AMSMI-RD-CS-R/DOCUMENTS BLDG. 4484	
PICATINNY ARSENAL, NJ 07806-5000		REDSTONE ARSENAL, AL 35898-5241	
DIRECTOR U.S. ARMY RESEARCH LABORATORY ATTN: AMSRL-DD-T, BLDG. 305	1	COMMANDER U.S. ARMY FOREIGN SCI & TECH CENTER ATTN: DRXST-SD	1
ABERDEEN PROVING GROUND, MD 21005-5066		220 7TH STREET, N.E. CHARLOTTESVILLE, VA 22901	
DIRECTOR U.S. ARMY RESEARCH LABORATORY ATTN: AMSRL-WT-PD (DR. B. BURNS)	1	COMMANDER U.S. ARMY LABCOM, ISA ATTN: SLCIS-IM-TL	1
ABERDEEN PROVING GROUND, MD 21005-5066		2800 POWER MILL ROAD ADELPHI, MD 20783-1145	
DIRECTOR U.S. MATERIEL SYSTEMS ANALYSIS ACTV ATTN: AMXSY-MP	1		
ABERDEEN PROVING GROUND, MD 21005-5071			

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER,
BENÉT LABORATORIES, CCAC, U.S. ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND,
AMSTA-AR-CCB-O, WATERVLIET, NY 12189-4050 OF ADDRESS CHANGES.

TECHNICAL REPORT EXTERNAL DISTRIBUTION LIST (CONT'D)

	<u>NO. OF COPIES</u>		<u>NO. OF COPIES</u>
COMMANDER		WRIGHT LABORATORY	
U.S. ARMY RESEARCH OFFICE		ARMAMENT DIRECTORATE	
ATTN: CHIEF, IPO	1	ATTN: WL/MNM	1
P.O. BOX 12211		EGLIN AFB, FL 32542-6810	
RESEARCH TRIANGLE PARK, NC 27709-2211			
DIRECTOR		WRIGHT LABORATORY	
U.S. NAVAL RESEARCH LABORATORY		ARMAMENT DIRECTORATE	
ATTN: MATERIALS SCI & TECH DIV	1	ATTN: WL/MNMF	1
WASHINGTON, D.C. 20375		EGLIN AFB, FL 32542-6810	

NOTE: PLEASE NOTIFY COMMANDER, ARMAMENT RESEARCH, DEVELOPMENT, AND ENGINEERING CENTER,
BENÉT LABORATORIES, CCAC, U.S. ARMY TANK-AUTOMOTIVE AND ARMAMENTS COMMAND,
AMSTA-AR-CCB-O, WATERVLIET, NY 12189-4050 OF ADDRESS CHANGES.
